*Emerging Technology Summary*

CP–AID
Concrete Pavement—Accelerated Implementation and Deployment Resources

AUGUST 2026

# T-FAST

## A NEW TEST METHOD TO ASSESS ALKALI-SILICA REACTION SUSCEPTIBILITY IN AGGREGATES

### WHAT IS ALKALI–SILICA REACTION?

Alkali-silica reaction (ASR) is a degradation mechanism that affects concrete infrastructure worldwide. ASR occurs in a concrete mixture when certain siliceous mineral phases within the aggregates react with the alkalis typically supplied by the cementitious materials. Certain products of this reaction, known as ASR gels, can absorb moisture and swell. This swelling, when ASR gels accumulate in sufficient quantities, can cause the concrete to crack, which reduces its service life. ASR is a complex reaction that generally takes 5 to 25 years to manifest in the field.

### HOW DO PRACTITIONERS ASSESS RISK OF ASR IN NEW CONSTRUCTION?

Traditionally, the concrete community has relied heavily on accelerated expansion testing to detect the ASR susceptibility of aggregates used in concrete. Practitioners use the information conveyed by various standard test methods, described below, to determine the risk of ASR for a given aggregate.

### COMMONLY USED ASR EXPANSION TEST METHODS AND THEIR LIMITATIONS

The most common expansion-based accelerated standard tests for assessing aggregate reactivity in the United States are the concrete prism test (CPT) described in ASTM C1293, the accelerated mortar bar test (AMBT) described in ASTM C1260 and its counterpart AASHTO T 303, and, to a lesser extent, the miniature concrete prism test (MCPT) described in AASHTO T 380. Unfortunately, factors such as the low sensitivity to some specific alkali-silica reactive phases (false negatives) in the AMBT, the nature of the “nonreactive” counterpart aggregate used in the CPT, and the influence of cement chemistry on the outcomes of all of these tests affect the reliability of these standards. As a result of these limitations, different laboratories may report different ASR classifications for the same aggregate, thus increasing the risk that inadequate mitigation strategies will be implemented when the tested aggregate is used in the field or that acceptable aggregates are rejected.

### T-FAST: A NEW CHEMICAL-BASED STANDARD

Provisional standard AASHTO TP 144 describes the Turner-Fairbank ASR Aggregate Susceptibility Test (T-FAST), a new testing protocol used to determine whether an aggregate contains alkali-silica reactive phases. T-FAST is a chemical test in which the aggregate (crushed in the case of coarse aggregate) is exposed to the main factors controlling ASR (alkalis, water, calcium, and temperature). Changes in the measured concentration of certain ions (calcium, aluminum, and silicon) in the test solution are used as indicators to predict the formation of ASR gel products. This test moves away from the need to physically mix, cast, and measure the expansion of concrete prisms and mortar bars, as shown in Figure 1.

T-FAST has been designed to be a detection tool for even trace amounts of reactive phases in aggregates but should not be used by itself to predict the field performance of concrete. Interested to know how to assess ASR field performance of a mixture? Read more in a related tech brief on alkali threshold testing.

National Concrete Pavement Technology Center
Tech Center

**AUTHOR**
Jose F. Munoz Campos,
Federal Highway Administration

Chandni Balachandran,
Advanced Global Resources

**SPONSOR**
Federal Highway Administration
Part of Cooperative Agreement
693JJ324NF00013, Development
and Deployment of Innovative
Technologies for Concrete Pavements

**NOTICE**
The mission of the National Concrete Pavement Technology Center (CP Tech Center) at Iowa State University is to unite key transportation stakeholders around the central goal of developing and implementing innovative technology and best practices for sustainable concrete pavement construction and maintenance.

Any opinions, findings, and conclusions or recommendations expressed in this publication are those of the author and do not necessarily reflect the view of the U.S. Department of Transportation or Iowa State University.

Iowa State University does not discriminate on the basis of race, color, age, ethnicity, religion, national origin, pregnancy, sexual orientation, genetic information, sex, marital status, disability, or status as a U.S. Veteran. Inquiries regarding nondiscrimination policies may be directed to Office of Equal Opportunity, 2680 Beardshear Hall, 515 Morrill Road, Ames, Iowa 50011, telephone: 515-294-7612, email: eooffice@iastate.edu.

**NATIONAL CONCRETE PAVEMENT TECHNOLOGY CENTER**
2711 South Loop Drive, Suite 4700
Ames, IA 50010-8664
cptechcenter.org
515-294-5798

National Concrete Pavement Technology Center

Tech Center

IOWA STATE UNIVERSITY
Institute for Transportation

CP—AID 26-02

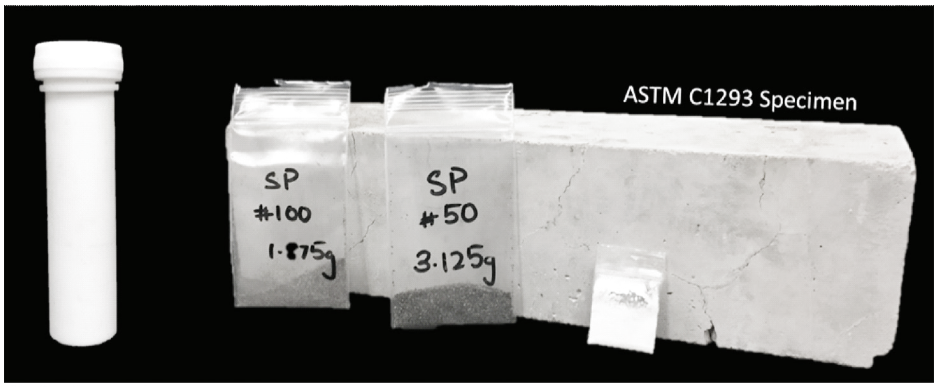


SP = Spratt aggregate

FHWA, used with permission

***Figure 1. Comparison between the T-FAST test tube setup and a typical concrete prism specified in ASTM C1293***

## WHY T-FAST?

T-FAST more accurately detects the presence of alkali-silica reactive phases in aggregates than the current ASR expansion tests. Its results are not influenced by the typical challenges associated with these tests. Because of its high sensitivity, T-FAST eliminates the risk of false negatives that affect the AMBT results. Unlike CPT, T-FAST evaluates the aggregate independently, eliminating the influence of nonreactive aggregates in the results. These advantages enable a safe assessment of aggregate reactivity. Additionally, T-FAST is efficient, with results achieved within 21 days. Given its high sensitivity and efficiency, T-FAST can be used as a powerful quality assurance tool.

## REFERENCES

Muñoz, J. F., C. Balachandran, and T. S. Arnold. 2021. New chemical reactivity index to assess alkali-silica reactivity of coarse aggregates. *Journal of Materials in Civil Engineering*, Vol. 33, No. 4, 04021037.

Muñoz, J. F., C. Balachandran, and T. S. Arnold. 2021. New Turner-Fairbank alkali-silica reaction susceptibility test for aggregate evaluation. *Transportation Research Record*, Vol. 2675, No. 9, pp. 798–808. https://doi.org/10.1177/03611981211004584.

Muñoz, J. F., C. Balachandran, M. Beyene, and T. S. Arnold. 2021. *A Novel Approach for the Assessment of ASR Susceptibility of Concrete Mixtures in Airfield Pavements and Infrastructure*. FHWA-HRT-21-103. Federal Highway Administration, Office of Research, Development, and Technology.

## ACKNOWLEDGMENTS

The National Concrete Pavement technology Center would like to acknowledge and thank the following individuals who took the time to review and comment on this Tech Brief:

Lieska Halsey (Nebraska Department of Transportation), Eric Giannini (American Cement Association), Maria Masten (Minnesota Department of Transportation), Sarah Lopez (NCE), Robert Spragg (Federal Highway Administration), and Paul Tennis (American Cement Association).